arXiv:cond-mat/0310497v1 [cond-mat.mtrl-sci] 21 Oct 2003

Angular Dependence of Switching Properties in Single Fe Nanopillars

G. Brown*
Center for Computational Sciences, Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA

S.M. Stinnett and M.A. Novotny†
Department of Physics and Astronomy and ERC Center for Computational Sciences,
Mississippi State University, Mississippi State, MS 39759, USA

P.A. Rikvold‡
Department of Physics, Center for Materials Research and Technology,
and School for Computational Science and Information Technology,
Florida State University, Tallahassee, FL 32306-4350, USA

(Dated: February 2, 2008)

The continued increase in areal densities in magnetic recording makes it crucial to understand magnetization reversal in nanoparticles. We present finite-temperature micromagnetic simulations of hysteresis in Fe nanopillars with the long axis tilted at angles from 0 degrees to 90 degrees to the applied sinusoidal field. The field period is 15 ns, and the particle size is $9 \times 9 \times 150$ nm. The system is discretized into a rectangular pillar of $7 \times 7 \times 101$ spins each with uniform magnetization. At low angles, reversal begins at the endcaps and proceeds toward the center of the particle. At ninety degrees, reversal proceeds along the entire length of the particle (save at the ends). The switching field was observed to increase over the entire range of angles, consistent with recent experimental observations. A second, lower-resolution micromagnetic simulation with $1 \times 1 \times 17$ spins, does not agree with experiment, but shows behavior very similar to that of the Stoner-Wohlfarth model of coherent rotation.

Keywords: Hysteresis, Micromagnetics

Hysteresis in magnetic particles has been studied for nearly a century. However, the increasing areal densities currently being pursued in magnetic recording technologies are pushing bit sizes to length scales where the atomic nature of materials is important. In addition, large data-transfer rates require switching times not much longer than the precession times of atomic moments. Taken together, further technological advances require a better understanding of hysteresis in nanoscale magnets at nanosecond time scales. Since these nanomagnets are often single-domain, the cooperative effects among the atomic spins determine the switching behavior. This cooperative behavior can be studied with simulations of realistic model systems, and can be directly compared to high-resolution experimental results,[1,2,3,4] possibly for individual nanomagnets.[4] In the present paper we present such dynamic simulations of hysteresis in nanometer-sized Fe nanopillars exposed to a magnetic field that is aligned at an angle with the pillars' long axis.

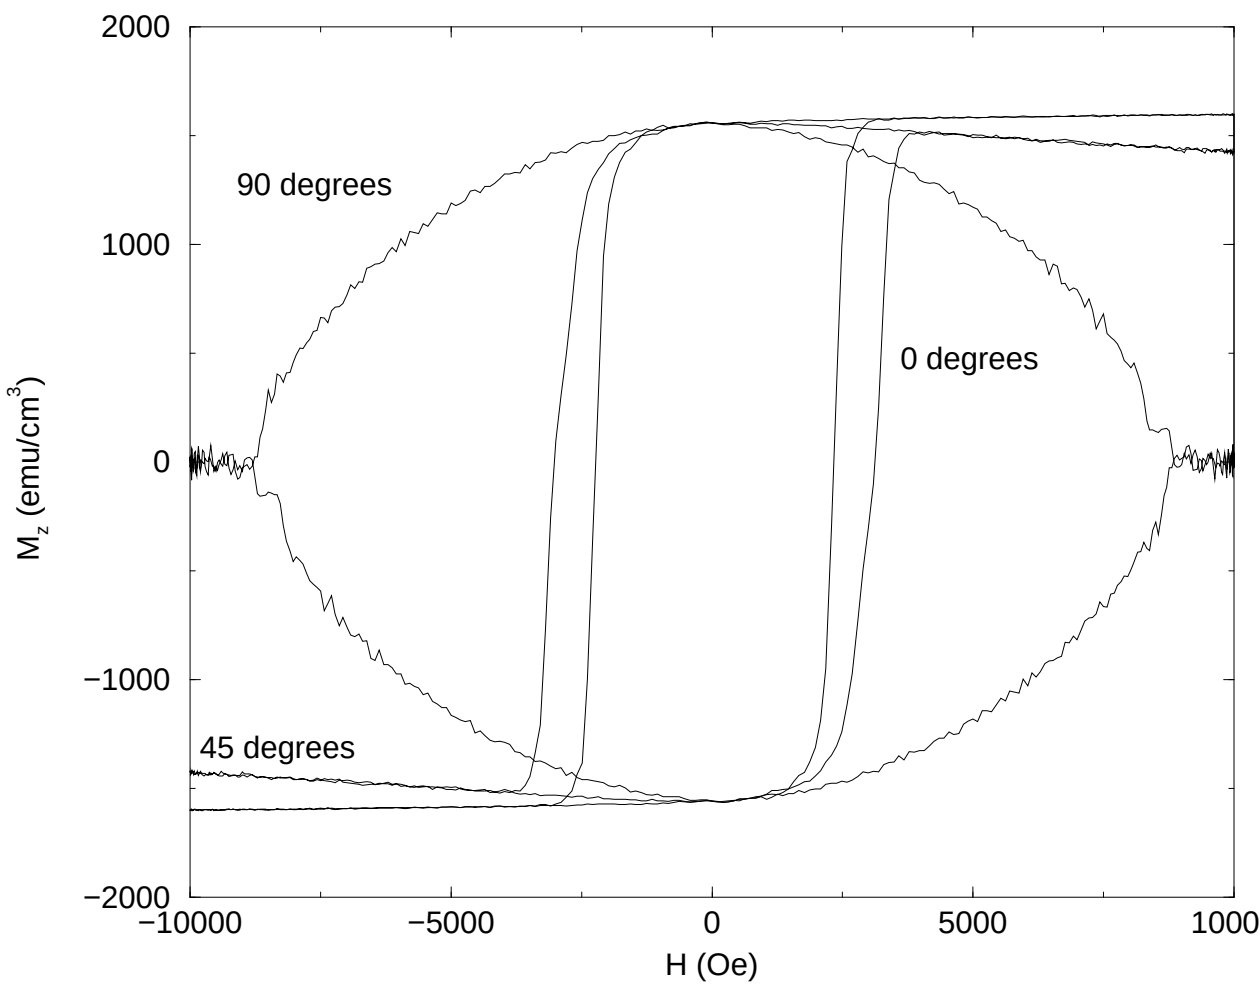

FIG. 1: Hysteresis Loops for the 4949-spin model with misalignment angles of 0°, 45°, and 90°. The applied field is sinusoidal with a period of 15 ns, and the temperature is $T = 100$ K. One half of a loop was calculated and the data reflected to show a complete loop.

The general method in micromagnetics simulations is to divide a model magnetic system into coarse-grained regions, each with a uniform magnetization density $\vec{M}(\vec{r}_i)$ of a constant magnitude, M_S. Here $\vec{r}_i$ is the position of the ith spin in the system. The time evolution of each spin is given by the Landau-Lifshitz-Gilbert (LLG) equation,[5,6,7]

$$\frac{d\vec{M}(\vec{r}_i)}{dt} = \frac{\gamma_0}{1+\alpha^2}(\vec{M}(\vec{r}_i) \times [\vec{H}(\vec{r}_i) - \frac{\alpha}{M_S}(\vec{M}(\vec{r}_i) \times \vec{H}(\vec{r}_i))]) \tag{1}$$

where $\vec{H}(\vec{r}_i)$ is the total local field at the ith position, γ_0 is the gyromagnetic ratio (1.76×10^7 rad/Oe s), and $\alpha = 0.1$ is a dimensionless damping parameter which determines the rate of energy dissipation. For the sign of the precession term, we follow the convention of Brown.[5]

The total local field, $\vec{H}(\vec{r}_i)$, includes contributions from the applied field, dipole-dipole fields, and exchange interactions;[6] here the small crystalline anisotropy of Fe

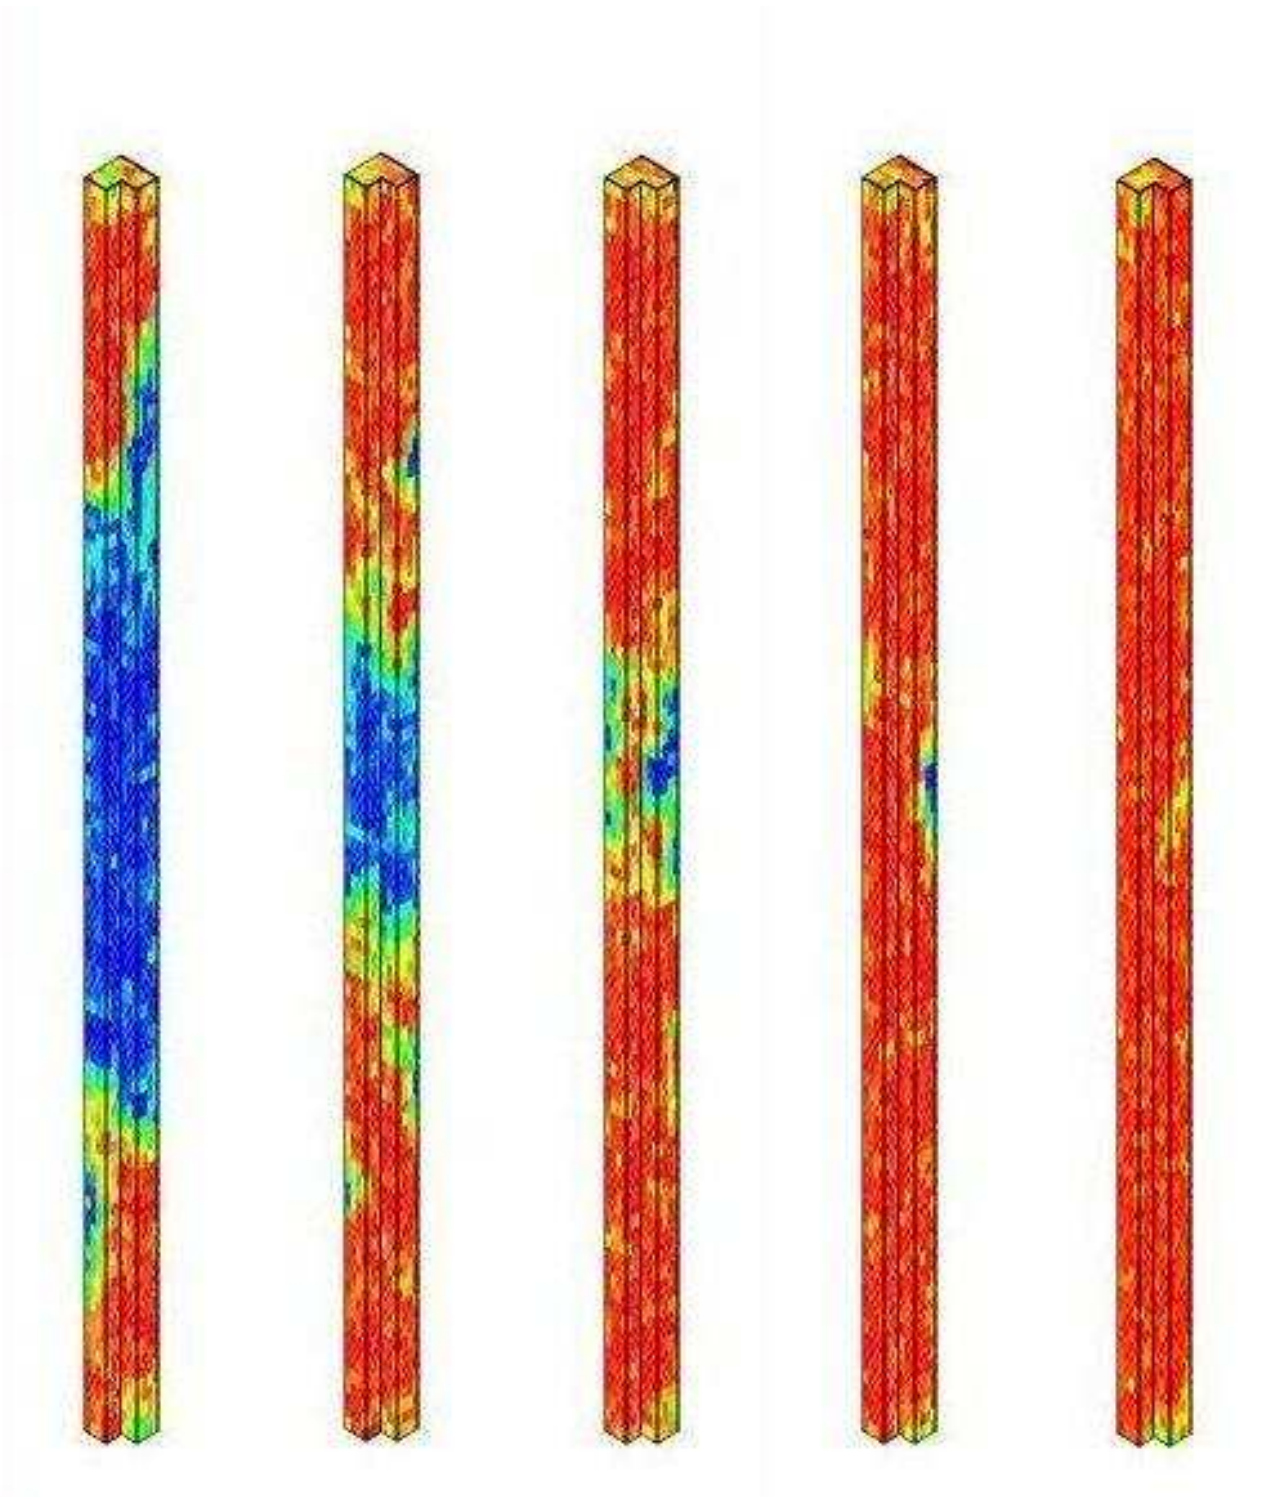

FIG. 2: The z-component of the magnetization at times t= 4.48, 4.53, 4.58, 4.63, and 4.68 ns during the switching process of the 45° hysteresis loop in Fig. 1.

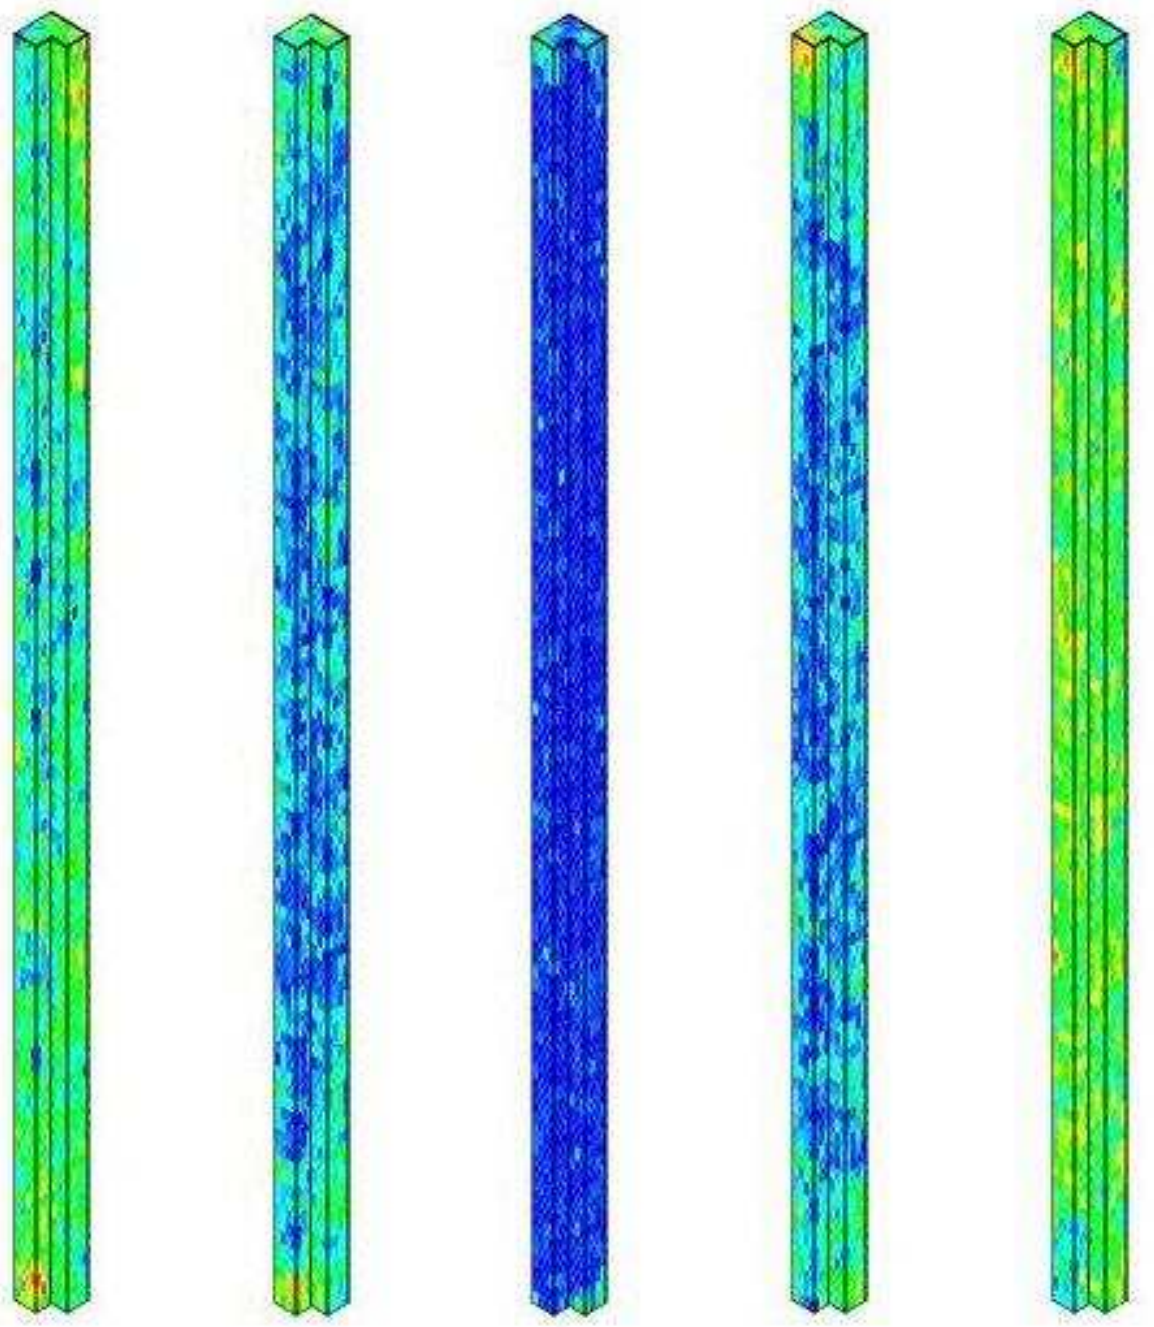

FIG. 3: The z-component of the magnetization at times t= 2.25, 3.75, 5.25, 6.00, and 6.75 ns during the relaxation process of the 90° hysteresis loop in Fig. 1.

is ignored. At nonzero temperatures, thermal fluctuations also contribute a term in the form of a stochastic thermal field which fluctuates independently for each spin. The thermal fluctuations are Gaussian with a mean of zero and covariance given by the fluctuation-dissipation theorem.[6]

We have used two different models to simulate hysteresis in single Fe nanopillars, as have been synthesized and studied by Wirth, *et al.*[1,2,3,4] The first model is a 9 nm×9 nm×150 nm pillar, discretized into a cubic lattice with 4949 sites (7×7×101). For such a large number of sites, direct calculation of the dipole-dipole interactions is impractical, and the Fast Multipole Method was employed, as described elsewhere.[6] The second model is a 5.2 nm×5.2 nm×88 nm Fe pillar discretized into a one-dimensional chain of 17 spins. This model assumes that deviations of the magnetization from uniformity over the cross-section of the pillar are negligible, as has been observed in Monte Carlo simulations.[7] For both models, the material properties were chosen to correspond to bulk Fe, with saturation magnetization $M_{\rm S}$=1700 emu/cm^3 and exchange length 2.6 nm.

Figure 1 shows hysteresis loops at $T = 100$ K for the first model with the field misaligned at 0°, 45°, and 90° to the long axis of the pillar. The loops were calculated using a sinusoidal field with a period of 15 ns, which started at a maximum value of 10,000 Oe. In all the loops shown here, the reported magnetization is the component along the long axis (z-axis) of the pillar. With the field and pillar aligned (0°), reversal initiates at the ends, as previously reported.[6] At 45° misalignment between pillar and field, the magnetization is initially pulled away from the long (easy) axis by the large magnetic field. As the field is swept toward zero, the magnetization relaxes until it essentially reaches saturation at zero applied field.

Figure 2 shows the z-component of the magnetization at selected times during the reversal process for the 45° hysteresis loop in Fig. 1. As with 0°, regions of reversed magnetization nucleate at the ends of the pillar, and it is the growth of these reversed regions that leads to magnetic reversal of the particle. It is important to note that the particles do not have a uniform magnetization, even though they are single-domain particles and would be in equilibrium under quiescent conditions.

For 90° misalignment, the reversal mechanism is quite different. The hysteresis loop in Fig. 1 shows that the magnetization is essentially perpendicular to the easy direction until the field reaches a particular value. As the field is decreased further, the magnetization relaxes toward the easy axis. Since nothing breaks the up/down symmetry of the system when the applied field has no component along the easy axis, the relaxed magnetization can be directed toward either the positive or negative z-axis. Figure 3 shows the z-component of the magnetization for the 90° misalignment at selected times during the hysteresis loop. For this case, the relaxation occurs

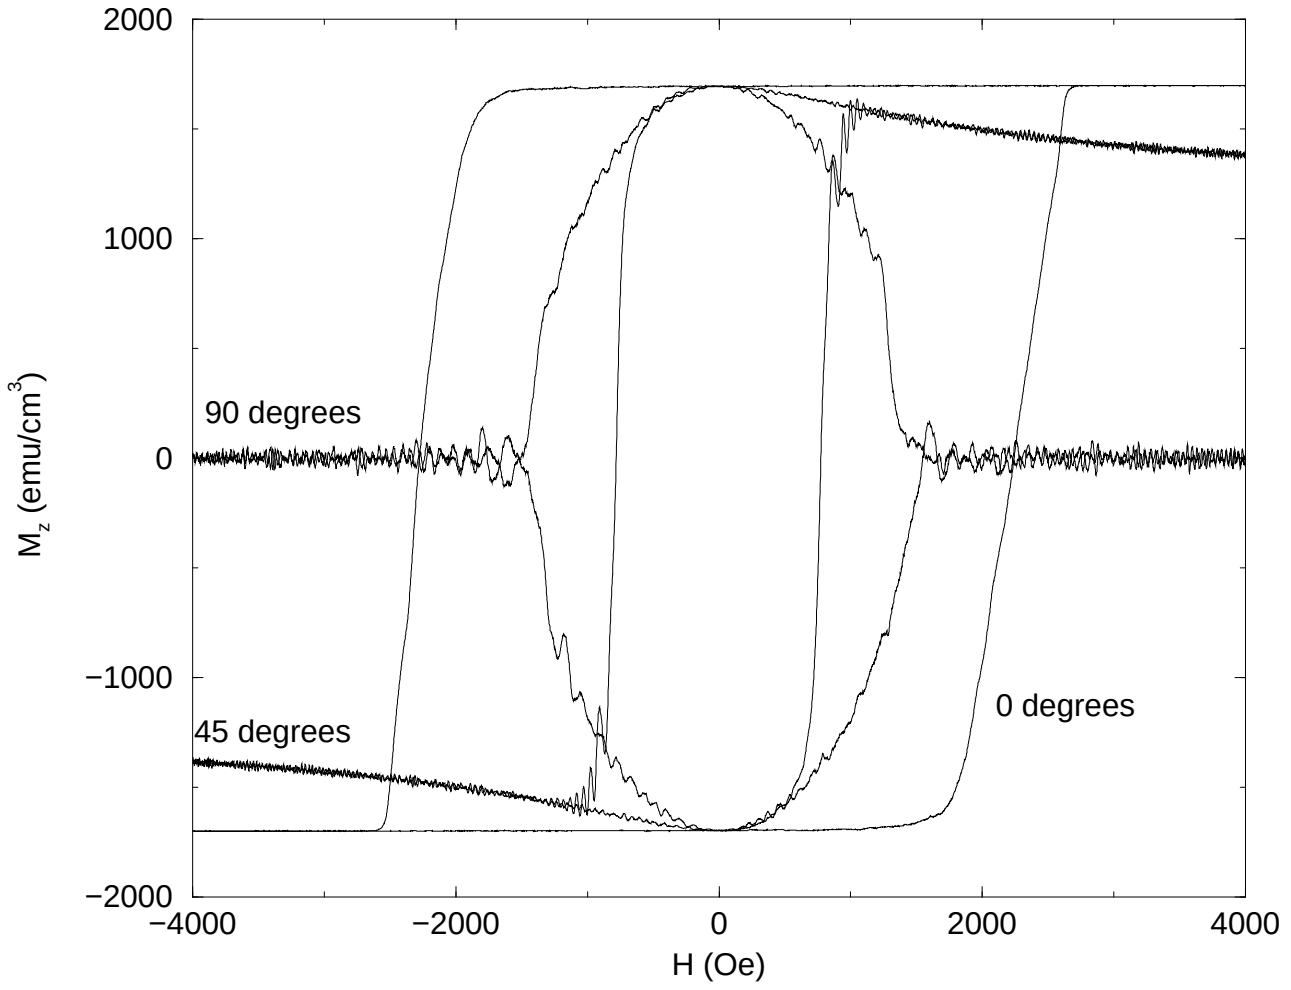

FIG. 4: Hysteresis loops at 0°, 45°, and 90° misalignment between the field and easy axis for the 17-spin model. The applied field is sinusoidal with period 200 ns, and $T = 10$ K. Qualitatively, the loop shapes appear similar to those for the 4949-spin model (Fig. 1), but the angular-dependence of the switching field for the two models is quite different.

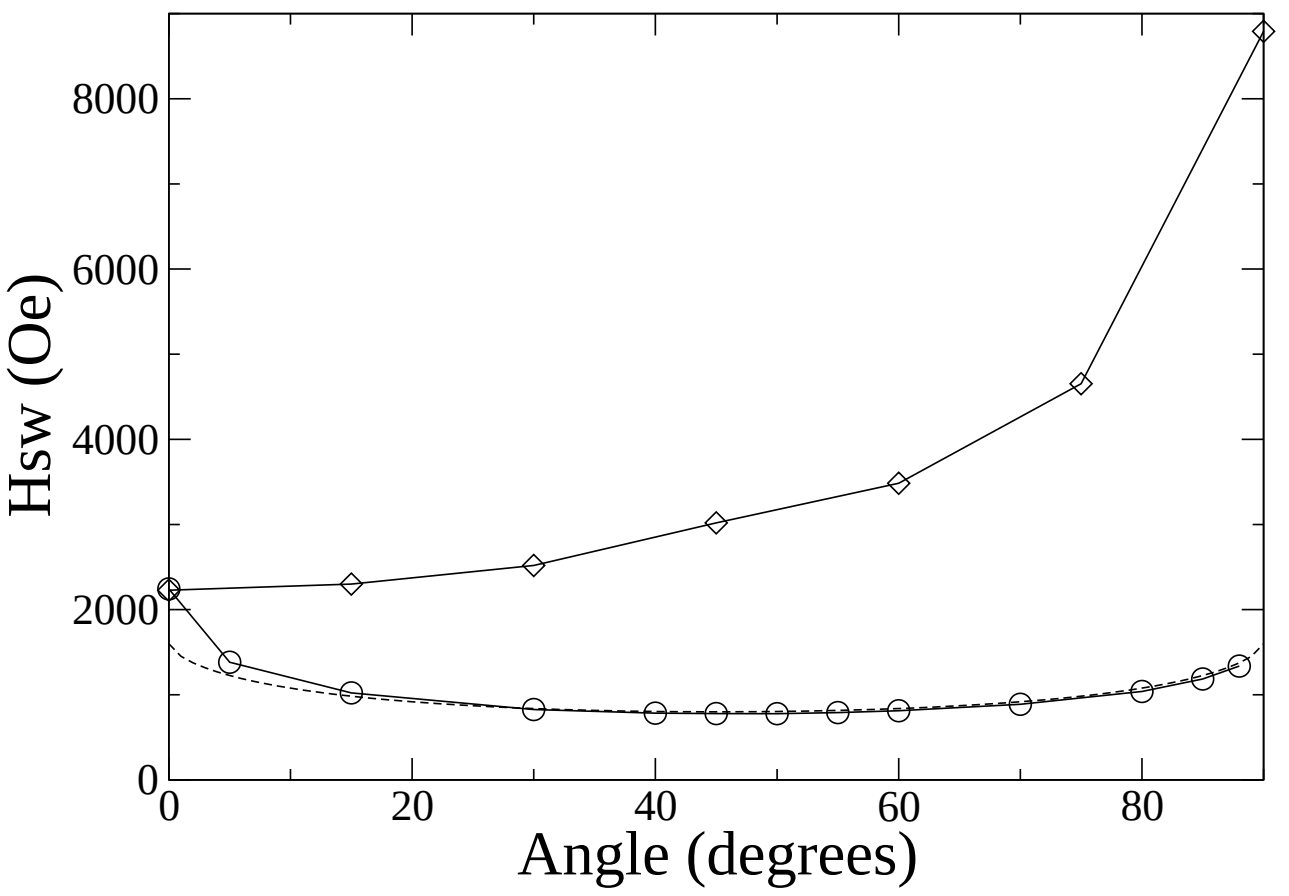

FIG. 5: The angular dependence of the switching field $H_{\rm sw}$, shown the 4949-spin model (diamonds) and the 17-spin model (circles). The shape for the 17-spin model is qualitatively similar to what is expected from the Stoner-Wohlfarth model (dashed curve), while the 4949-spin model yields a dependence more consistent with recent experiments.

along the entire length of the pillar, except at the ends. The pole-avoidance effect present at the ends, and involved in nucleation at smaller angles, retards relaxation along the easy axis.

The hysteresis loops for the second, smaller model shown in Fig. 4 are qualitatively similar to those of Fig. 1. Again loops at 0°, 80°, and 90° misalignment are shown. There are important differences between the two models, however. First, without lateral resolution of the magnetization across the cross-section, these pillars exhibit ringing due to the processional dynamics. Evidently, the precession of individual moments in the 4949-spin model does not lead to precession of the end-cap moment; possibly the spin waves rapidly damp out the gyromagnetic motion. A second, and more prominent, difference between the models is observed in the angular dependence of the switching field, $H_{\rm sw}$, shown in Fig. 5. Here $H_{\rm sw}$ is defined as the applied field at which $M_z = 0$ (or in the case of 90° misalignment, where $M_z \neq 0$). The second model (circles) shows a shape qualitatively similar to what is expected from Stoner-Wohlfarth (SW) theory, with a minimum $H_{\rm sw}$ at 45°. The dashed curve is the SW theory with H_k=1600 Oe, much smaller than the 10^4 Oe assumed for ellipsoids. The first model (diamonds), on the other hand, has minimum $H_{\rm sw}$ at 0°, and increases as the misalignment angle is increased. This behavior is consistent with recent experimental observations of Fe nanopillars.[1,3,4]

In summary, we have presented results from large-scale, finite-temperature micromagnetics simulations of hysteresis in models of nanometer-sized Fe pillars in magnetic fields inclined with respect to the long axis of the pillars. In a model in which the magnetization is constant across the short dimension of the pillar, the angular dependence of the switching field is similar to that expected from Stoner-Wohlfarth theory. However, in a model with spatial resolution across the short dimension, the switching field has a monotonically increasing angular behavior consistent with recent experimental results.

We acknowledge support from NSF grant No. DMR-0120310 and the DOE Office of Science through the Computational Material Science Network of BES-DMSE.

---

[*] browngrg@csit.fsu.edu; Also at CSIT, Florida State University, Tallahassee, FL 32306, USA

[†] man40@ra.msstate.edu

[‡] rikvold@csit.fsu.edu

[1] S. Wirth, M. Field, D.D. Awschalom, and S. von Molnár, Phys. Rev. B **57**, R14028 (1998).

[2] S. Wirth and S. von Molnár, J. Appl. Phys. **85**, 5249 (1999).

[3] Y. Li, P. Xiong, S. von Molnár, Y. Ohno, and H. Ohno, Appl. Phys. Lett. **80**, 4644 (2002).

[4] Y. Li, P. Xiong, S. von Molnár, Y. Ohno, and H. Ohno, J. Appl. Phys. **93**, 7912 (2003).

[5] W. Brown, *Micromagnetics* (Wiley, New York, 1963).

[6] G.Brown, M.A. Novotny and P.A. Rikvold, Phys. Rev. B **64**, 134432 (2001).

[7] U. Nowak, in *Annual Reviews of Computational Physics IX*, edited by D. Stauffer (World Scientific, Singapore, 2001), p. 105.